


49N

Multifunctional Epoxy Low-Flow Prepreg

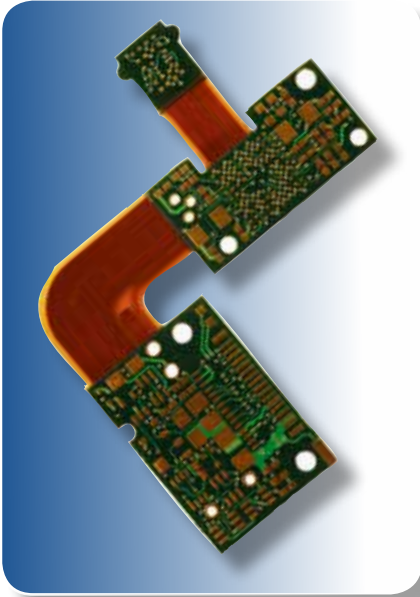


49N is a low-flow epoxy prepreg engineered for bonding multilayer epoxy rigid-flex or attaching heat-sinks to multilayer epoxy PCBs. With a high Tg, the prepreg can be used in high-performance or high-temperature applications compared to a standard difunctional epoxy low-flow.

Features:

- Multifunctional epoxy resin system with a Tg of 170°C offers improved high-temperature and PTH reliability
- Engineered with discrete low ranges and various fiberglass styles to optimize flexibility
- Electrical and mechanical properties meeting the requirements of IPC-4101/26, modified to be “Low-Flow”
- RoHS/WEEE compliant
- Short cure (45 minutes at 360°F) for improved manufacturing productivity

Typical Applications:

- Bonding multilayer epoxy rigid-flex
- Bonding adhesiveless epoxy rigid-flex
- Attaching heat sinks to multilayer PCBs

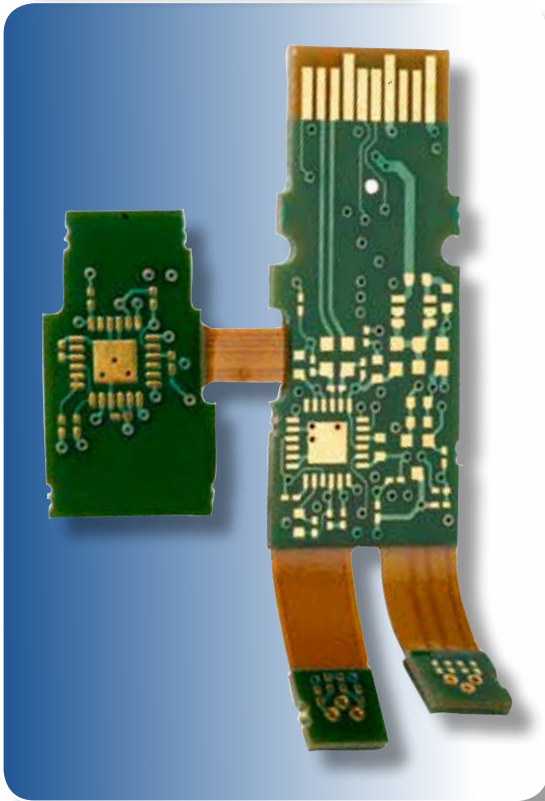

ARLON
ELECTRONIC MATERIALS

Typical Properties:

Property	Units	Value	Test Method
1. Electrical Properties			
Dielectric Constant			
@ 1 MHz	-	4.3	IPC TM-650 2.5.5.3
@ 1 GHz	-		IPC TM-650 2.5.5.9
Dissipation Factor			
@ 1 MHz	-	0.022	IPC TM-650 2.5.5.3
@ 1 GHz	-		IPC TM-650 2.5.5.9
Volume Resistivity			
C96/35/90	MΩ-cm	5.1×10^7	IPC TM-650 2.5.17.1
E24/125	MΩ-cm	7.4×10^7	IPC TM-650 2.5.17.1
Surface Resistivity			
C96/35/90	MΩ	8.8×10^6	IPC TM-650 2.5.17.1
E24/125	MΩ	1.5×10^6	IPC TM-650 2.5.17.1
Electrical Strength	Volts/mil (kV/mm)	1000 (39.4)	IPC TM-650 2.5.6.2
Dielectric Breakdown	kV		IPC TM-650 2.5.6
Arc Resistance	sec		IPC TM-650 2.5.1
2. Thermal Properties			
Glass Transition Temperature (Tg)			
TMA	°C		IPC TM-650 2.4.24
DSC	°C	170	IPC TM-650 2.4.25
Decomposition Temperature (Td)			
Initial	°C	296	IPC TM-650 2.3.41
5%	°C	325	IPC TM-650 2.3.41
T260	min	18	IPC TM-650 2.4.24.1
T288	min		IPC TM-650 2.4.24.1
T300	min		IPC TM-650 2.4.24.1
CTE (X,Y)	ppm/°C	16	IPC TM-650 2.4.41
CTE (Z)			
< Tg	ppm/°C	85	IPC TM-650 2.4.24
> Tg	ppm/°C		IPC TM-650 2.4.24
z-axis Expansion (50-260°C)	%		IPC TM-650 2.4.24
3. Mechanical Properties			
Peel Strength to Copper (1 oz/35 micron)			
After Thermal Stress	lb/in (N/mm)	9.0 (1.6)	IPC TM-650 2.4.8
At Elevated Temperatures	lb/in (N/mm)		IPC TM-650 2.4.8.2
After Process Solutions	lb/in (N/mm)		IPC TM-650 2.4.8
Young's Modulus	Mpsi (GPa)	2.6 (17.9)	IPC TM-650 2.4.18.3
Tensile Strength CD/MD	kpsi (MPa)	6.5 (45)	IPC TM-650 2.4.18.3
Poisson's Ratio	-	0.17	ASTM D-3039
4. Physical Properties			
Water Absorption (0.062")	%	0.1	IPC TM-650 2.6.2.1
Specific Gravity	g/cm ³	1.65	ASTM D792 Method A
Thermal Conductivity	W/mK	0.25	ASTM E1461
Flammability	class	V0	UL-94

Results listed above are typical properties, provided without warranty, expressed or implied, and without liability. Properties may vary, depending on design and application. Arlon reserves the right to change or update these values.

Availability:

Arlon Part Number	Glass Style	Resin %	Flow	Thickness
49N067201	106	72	0.030" – 0.090"	0.0023"
49N806501	1080	65	0.030" – 0.090"	0.0034"
49N067202	106	72	0.060" – 0.120"	0.0023"
49N806502	1080	65	0.060" – 0.120"	0.0034"

Recommended Process Conditions:

Process inner-layers through develop, etch, and strip using standard industry practices. Bake inner layers in a rack for 60 minutes at 225°F - 250°F (107°C - 121°C) immediately prior to lay-up. Vacuum desiccate the prepreg for 8 - 12 hours prior to lamination.

Lamination Cycle:

- 1) Pre-vacuum for 30 - 45 minutes
- 2) Control the heat rise to 8°F - 12°F (4°C - 6°C) per minute between 150°F and 250°F (65°C and 121°C)
- 3) Lamination Pressure: 150-300 PSI (11-21 Kg/cm²) depending on complexity
- 4) Product temperature at start of cure = 360°F (182°C).
- 5) Cure time at temperature = 45 minutes
- 6) Cool down under pressure at ≤ 10°F/min (6°C/min)

Drill at 350-400 SFM. Undercut bits are recommended for vias 0.023" (0.9cm) and smaller

De-smear using alkaline permanganate or plasma with settings appropriate for epoxy; plasma is preferred for positive etchback

Conventional plating processes are compatible with 49N

Standard profiling parameters may be used; chip breaker style router bits are not recommended

Bake for 1 - 2 hours at 250°F (121°C) prior to solder reflow or HASL

49N

Arlon Electronic Materials...
CHALLENGE US!

For samples, technical assistance and customer service, please contact Arlon Electronic Materials Division at the following locations:

NORTH AMERICA:

Arlon EMD, 9433 Hyssop Drive, Rancho Cucamonga, CA
Tel: (909) 987-9533 • Fax: (909) 987-8541

FRANCE:

CCI Eurolam
9, rue Marcelin Bertholet
92160 Antony, France
Phone: (33) 146744747
Fax: (33) 146666313

ISRAEL:

Tech Knowledge, Ltd.
159 Yigal Alon Street,
Tel Aviv 6744367, Israel
Phone: (972) 36958117
Fax: (972) 36917117

CHINA:

Zack Peng
Room 6A, Unit 2, Bldg 2
Jin Cheng Shi Dai, Tian Road
Shenzhen, China 518103
Phone: (86) 75528236491
Fax: (86) 75528236463

GERMANY:

CCI Eurolam
Otto-Hahn-Str. 46
63303 Dreiech Germany
Phone: (49) 610339920
Fax: (49) 6103399229

ITALY:

Dralmi, SAS
Via Cellini 5
20129 Milano Italy
Phone: (39) 025460507
Fax: (39) 0255013199

JAPAN:

Nakao Corp.
12-8 Nihonbashi Hisamatsu-Cho
Tokyo 103-0005 Japan
Phone: (81) 336623201
Fax: (81) 336617118

UK & SCANDINAVIA:

CCI Eurolam – UK
Ulness Walton Lane
Leyland, PR26 8NB, UK
Phone: (44) 1772452236
Fax: (44) 1772456859